

LANXESS

Energizing Chemistry

Baypren®

Chloroprene, the first class
all-round performer
for a wide range of applications

Edition 2010-10





High pressure? Ultra high pressure?
For highest requirements:
Hydraulic hoses made of Baypren®.

What is Baypren®	4
Historical overview	5
Properties of Baypren®	6
Crystallization	6
Modification	6
Properties of vulcanizates based on Baypren®	7
Aging and heat resistance	7
Weathering and ozone resistance	7
Resistance to water and chemicals	7
Resistance to fungi and bacteria	7
Abrasion resistance	7
Resilience	7
Dynamic fatigue resistance	7
Deformation properties	7
Combustion behavior	7
Low-temperature flexibility	8
Electrical properties	8
Thermal conductivity and coefficient of thermal expansion	8
Gas permeability	8
Baypren® applications in the automotive and general industry	10
Hoses	10
Molded parts	10
Conveyor and transmission belts	10
Other	10
Baypren® applications in the building industry and in the cable and wire industry	11
Baypren® product range	12
Baypren® service and contact data	13
Quality and safety	14
Responsible Care	15

Front page:

Dampers and bearings made of Baypren® are extremely durable for an extremely long time

What is Baypren®?

About Baypren®

Chloroprene rubber (international abbreviation: CR) is a high-performance material with a wide diversity of applications. Along with Bayer's other synthetic rubber products, Baypren® has been produced and distributed by LANXESS AG since 2005. In April 1957, Bayer became the first company to manufacture CR in Europe when it opened its production plant in Leverkusen, Germany. Since then, in addition to making ongoing improvements to the production process and developing products to match market requirements, the company has placed special emphasis on the development of new applications for Baypren®. Process and application-oriented formulations have been developed for modern manufacturing methods and for a large number of end-uses. The formulations and the properties of the individual products have been constantly adapted to meet the more challenging requirements of today's production processes and end-users.



Supply forms of Baypren®: solid rubber grades

Baypren® is the name of the LANXESS range of polymers based on 2-chloro-1,3-butadiene (chloroprene), which are manufactured by water-based emulsion polymerization in the presence of emulsifiers, activators etc. The importance of Baypren® is derived essentially from its attractive combination of key technical properties that is unmatched by any other kind of rubber at a comparable price. This has led to the development of many product variants to meet diverse requirements.

Articles made from appropriately formulated Baypren® compounds are suitable for moldings and extrudates of all types, reinforced hoses, roll covers, belting, including conveyor belts, air spring bellows, cable sheathing and insulation for low-voltage cables, sponge rubber, including open and closed-cell sponge rubber, corrosion-resistant linings, sheeting, fabric proofings and footwear (boots). The flame-retardant behavior of Baypren® vulcanizates can be adjusted to meet special requirements. Since 2005 Baypren® has been produced and distributed together with the other technical rubber products by LANXESS AG.

A key position – from the beginning until today

Bayer began producing chloroprene rubber in April 1957, and the first production line in Leverkusen had a capacity of 2,400 metric tons per year. The special-purpose rubber – which was first marketed under the trade name Perbunan® C and changed its name to Baypren® in 1968 – has occupied a key position on the world rubber market ever since with its wide range of applications. Although Baypren® was initially manufactured in Leverkusen, production was gradually relocated in the early sixties to another Bayer site in Germany, namely Dormagen. In 1975, Bayer began chloroprene rubber production using a modern system based on its own raw materials when a large-scale plant was built at the Dormagen site to manufacture chloroprene monomer.

The latest major step in the history of chloroprene rubber took place in 2005 when the Baypren® rubber activities were transferred to LANXESS AG.

The history of Baypren®

1957	Bayer begins the first European production of CR in Leverkusen, Germany under the trade name Perbunan® C (solid rubber, adhesive grades, latex)
1960	Gradual relocation of production to Dormagen, Germany
1968	CR renamed Baypren®
1975	Establishment of Bayer's own supply of monomer at Dormagen
2005	Transfer to LANXESS AG

Production with state-of-the-art PCS

The CR plant in Dormagen produces polychloroprene by the continuous emulsion polymerization process. This results in high-quality polymers for technical rubber, adhesive and latex applications. The monomers are produced on site by LANXESS based on the butadiene gas phase process, with the chlorine and butadiene delivered by pipeline from on-site suppliers.

Several investments have been made recently to increase capacity and improve the quality and safety of the production plant in Dormagen. A major project was the implementation of a new Process Control System (PCS) in the polymerization plant in which a central control room for the whole production unit was built. Since November 2006, it has been possible to control the monomer production unit, the polymerization, the finishing and the creaming farm from this control room, significantly increasing the efficiency of the CR plant. The state-of-the-art PCS plays a major role in improving the safety and quality of CR production.

The capacity of adhesive grade production will be increased before the end of 2007 through further investment in polymerization reactors. In addition, the capacity of the creaming farm has already been increased – including the creaming and degassing steps. Further investment in that area will double the capacity of our dispersion product line by mid-2008.



Part of the Baypren® production plant in Dormagen, Germany

Properties of Baypren®

Crystallization

A key distinguishing feature of the raw polymers is their tendency to crystallize. While virtually all liquids – water, for example – have a clearly defined temperature at which they undergo spontaneous crystallization on cooling (solidification point), some high molecular-weight products, such as natural rubber and a number of synthetic rubber grades, do not have a clearly defined crystallization point. Instead, they harden slowly as the temperature falls.

In case of these rubber grades, this behavior is caused by a partial orientation of the macromolecules (crystallization). This hardening overlaps the increase in hardness that results from a drop in temperature (thermoplasticity). Hardening due to crystallization is a fully reversible process that can be performed by subjecting the crystallized material to heat or dynamic stress. Unvulcanized polymers and compounds display a strong tendency to crystallize. Vulcanization, however, considerably slows down the extent of hardening resulting from crystallization in rubber articles.

The tendency of the polymers to crystallize can be influenced by appropriately controlled production processes. For this reason, rubber articles made from Baypren® grades with a low tendency to crystallize display virtually no increase in hardness due to crystallization even after exposure to low temperatures for long periods. In contrast, polymers with a particularly pronounced tendency to crystallize display a clear increase in hardness even after a relatively short time.

Modification

The properties of Baypren® vulcanizates are influenced by the type of modification of the raw polymer.

Effect of pre-crosslinking

- reduction of the elastic resilience (snappiness) of the raw rubber and uncured compound
- reduction of the die swell
- improvement in calendering behavior
- improvement of the surface smoothness of injection-molded articles
- improvement of the dimensional stability, e.g. of uncured profiles

Effect of sulfur modification

- facilitates mastication of the rubber, permitting the production of soft compounds with good building tack
- only MgO/ZnO required for vulcanization
- better tear resistance than standard grades
- better adhesion to fabrics than standard grades
- lower storage stability of raw polymers
- lower aging resistance of vulcanizates

Effect of XD (xanthogen disulfide) modification

- lower elasticity (less “nerve”) means easier processing (by calendering or extrusion)
- better mechanical properties than M-modified grades in the same formulation
- higher filler loadings possible



Dampers, which you can rely on

Properties of vulcanizates based on Baypren®

With the correct formulation, finished products made of Baypren® display the following characteristic properties in addition to their excellent rubber-elastic behavior:

- resistance to weathering, both in dry and humid climates
- excellent combustion behavior
- average resistance to oils
- aging and heat resistance
- good tensile strength, tear and wear resistance
- high dynamic fatigue resistance
- resistance to water and a large number of chemicals over a long period
- good adhesion to suitably pretreated reinforcing substrates consisting of textiles, metals or glass fibers
- resistance to fungi and soil bacteria
- low gas permeability
- electrical properties sufficient for a large number of applications

The suitability of a Baypren® compound for a particular application should be established by relevant testing. Thanks to its excellent set of properties, Baypren® is being used for the production of highly stressed rubber articles in many sectors, primarily in the automotive industry, mechanical engineering, plant construction, ship-building, mining and mineral oil production. The properties of Baypren® vulcanizates are influenced by the type of modification of the raw polymer (see above).

Aging and heat resistance

Baypren® vulcanizates display excellent aging resistance, especially those with an optimized antioxidant content. They neither soften nor harden at high temperatures or over long periods of stressing and remain elastic and serviceable. The heat resistance of Baypren® vulcanizates is considerably better than that of natural rubber vulcanizates. It corresponds roughly to the heat resistance of nitrile rubber.

Weathering and ozone resistance

While vulcanizates produced from many other rubber types tend to crack and harden relatively quickly and degrade when exposed to weathering and/or ozone, suitably formulated Baypren® vulcanizates do not exhibit any significant deterioration, even after many years of exposure to atmospheric influences such as light, rain, industrial gases and oxygen. By extrapolating the change in mechanical properties after many years of weathering in an ozone-rich atmosphere, it can be concluded, on the basis of current technology, that technical rubber goods made of Baypren® can be expected to display sufficient elasticity for the majority of static applications (for example structural profiles) after more than 50 years.

Resistance to water and chemicals

By employing specially formulated compounds, it is possible to obtain Baypren® vulcanizates that are resistant to water, acids, alkaline solutions and a large number of industrial chemicals. With a good resistance to hydrocarbons, Baypren® vulcanizates show sufficient

performance in contact with mineral oils to make them suitable for many applications. The corresponding volume change in mineral oils decreases with increasing naphthenic and, in particular, aliphatic content of the oil. Baypren® vulcanizates cannot match the very high swelling resistance to hydrocarbons of similarly formulated nitrile rubber vulcanizates, but their swelling resistance is considerably better than that of vulcanizates based on styrene-butadiene rubber, natural rubber or ethylene-propylene rubber.

Resistance to fungi and bacteria

Items made of rubber that are in contact with soil for long periods of time are susceptible to attack by soilborne bacteria and fungi. In the long term, this can lead to underground cables, for example, being destroyed. In contrast to the majority of other rubber types, Baypren® displays superior resistance to these microorganisms. This resistance can be enhanced still further through suitable compound formulation.

Abrasion resistance

Baypren® vulcanizates are highly wear-resistant. Their abrasion resistance is similar to that of nitrile rubber.

Resilience

Suitably formulated Baypren® vulcanizates possess very good resilience, although they do not attain the level of natural rubber. Very good resilience values are achieved in vulcanizates with a relatively high hardness.

Dynamic fatigue resistance

Baypren® vulcanizates are highly resistant to dynamic fatigue. Special grades are available to meet extremely stringent specifications, such as those applied to drive belts. The loss factor and hence the heat build-up under dynamic load are low.

Deformation properties

Baypren® vulcanizates have a low compression set over a temperature range of -10 to +145 °C. The low-temperature compression set is a key value employed in the assessment of vulcanizates for use in seals. At higher temperatures, where aging also plays a role, the compression set curves are lower than those of a large number of other elastomers.

Combustion behavior

Baypren® vulcanizates can be compounded for improved combustion behavior. The good combustion behavior of the polymer itself means that even stringent end-user specifications can be met. Limiting oxygen index (LOI) values in excess of 50 % can be attained with Baypren®. The requirements placed on the flame retardance of conveyor belts for underground mining applications can be met with properly compounded Baypren®.

Properties of Baypren®

Low-temperature flexibility

The glass transition temperature of unfilled Baypren® polymers remains fairly constant at around -34 °C, almost irrespective of the polymers' tendency to crystallize. The brittleness temperature and the glass transition temperature of Baypren® vulcanizates can be reduced to below -50 °C by appropriate compound formulation. Where rubber parts made of Baypren® are required to remain flexible at low temperatures over long periods, grades with a low crystallization tendency are recommended.

Electrical properties

Baypren® is highly suitable for cable sheathing and, in many cases, for low-voltage insulation. It is recommended for use in cables that must have resistance to weathering, ozone, oil and aging as well as good combustion resistance.

Thermal conductivity and coefficient of thermal expansion

The thermal conductivity and coefficient of thermal expansion of Baypren® vulcanizates are comparable with other elastomers (see comparison on opposite page). The values obtained are, of course, largely determined by the compound formulation. The thermal insulation is also similar to that of the majority of plastics used in the construction industry today.

Gas permeability

Baypren® vulcanizates have a very low gas permeability, which is roughly equivalent to that of nitrile rubber (see comparison on opposite page).



Low-temperature flexibility over long periods of time

Comparison of the gas permeability coefficient of Baypren® vulcanizates and other elastomers

Elastomers based on	Gas permeability 10 ⁻⁹ (cm ² s ⁻¹ bar ⁻¹)					
	Air		Nitrogen		Carbon dioxide	
	60 °C	80 °C	60 °C	80 °C	60 °C	80 °C
Chloroprene rubber (Baypren®)	70	120	45	80	580	760
Nitrile rubber (Perbunan® NT, Krynac®)	25 to 75	55 to 210	10 to 40	25 to 70	300 to 580	480 to 970
Natural rubber	250	400	180	330	1600	2100
Styrene-butadiene rubber (Krylene®)	150	260	110	200	1200	1500
Butyl rubber (Lanxess Butyl®)	20	50	15	35	130	290

Comparison of thermal conductivity according to VDE 0304/1 and the coefficient of linear expansion at 20-100 °C of Baypren® vulcanizates and vulcanizates based on other polymers

Elastomers based on	Thermal conductivity (kJm ⁻¹ h ⁻¹ °C ⁻¹)	Coefficient of thermal expansion 10 ⁻⁶ (mm°C ⁻¹)
Chloroprene rubber (Baypren®)	0.84	130-150
Nitrile rubber (Perbunan® NT, Krynac®)	0.92	150
Natural rubber	0.78	180
Styrene-butadiene rubber (Krylene®)	0.88	180
Butyl rubber (Lanxess Butyl®)	0.65	130

Baypren® applications in the automotive and general industry



High-performance grades for high-tech hydraulic hoses



Quality-solutions, worthwhile in any case



Powerfull rubber for power transmission belts



Discovering fascinating worlds with Baypren®

Hoses

- Hydraulic hoses for high pressure and ultra-high pressure
- Reinforced hoses for medium pressure and low pressure
- Brake hoses
- Oil and fuel hoses
- Hoses for use in the petroleum industry
- Floating hoses

Molded parts

- Bellows and dust caps
- Axle boots
- Round-section sealing strips, O-ring seals and flat seals
- Membranes
- Air springs
- Dampers and bearings with and without metal inserts, e.g. load bearing pads for high buildings and bridges
- Windshield wiper blades

Conveyor and transmission belts

- Power transmission belts for the automotive and general industry
 - Timing belts
 - Poly-V-belts
 - Raw-edge V-belts
 - Jacketed V-belts
- Conveyor belts with steel cord and textile reinforcement for underground mining applications, steel works, mineral processing plants and the chemical industry

Other


- Foam rubber sheet for wet suits and for the production of punched seals
- Covers for rollers in the printing industry and also in the textile and paper sectors
- Rubberized fabrics for all types of tarpaulins, containers and boats, and membranes in the automotive sector

Sealing strips

- Solid and microcellular rubber sealing strips for windows, doors and tailgates in the automotive sector
- Solid and microcellular rubber sealing strips for window and facade elements in the construction industry
- Expansion joint seals for civil engineering applications



Baypren® - the brand, you can build on

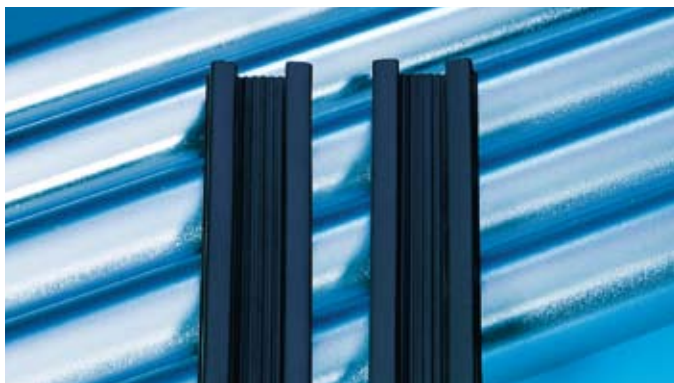

In construction elements Baypren® is in its element

Cables and wires

- Rubber-sheathed flexible cables for heavy-duty applications in hoisting gear and transport and conveyer systems
- Rubber-sheathed flexible cables for heavy-duty applications in underground and surface mining applications
- Rubber-sheathed flexible cables for use in dry and wet conditions on domestic appliances and light-duty workshop equipment; suitable for moderate service conditions
- Rubber-sheathed flexible cables with suspension unit for elevators and conveyer systems; suitable for moderately severe conditions
- Trailing cables for use in dry and wet conditions and also in underground applications where service conditions are severe
- Theater cables for mobile light fittings and light support structures
- Welding cables
- Flat flexible power and control cables for use in dry and wet conditions and also outdoors, especially for hoisting gear, transport systems, machine tools and processing machines; suitable for moderately severe conditions
- Flat flexible lighting cables



For use in dry or wet conditions – Baypren® cables and wires offer best conditions

Baypren® product range

Product	Crystallization	Mooney viscosity ⁽¹⁾ ML (1+4) 100°C	Density (g/cm ³)	Physical form	Packaging	Remarks
General purpose grades						
M-modified grades						
Baypren® 110	very low	41 +/-5	1.23	ivory-colored chips	25 kg paper bags with PE inner bags (0.05 mm thick, Vicat softening point DIN 53 460, ca. 75°C); 40 bags pallet = 1.000 kg net / 35 bags pallet = 875 kg net. Also available only on request: 20 kg PE bags; 50 bags per pallet = 1.000 kg net / 40 bags per pallet = 800 kg net / 25 kg PE bags 40 bags per pallet = 1000 kg net	
Baypren® 110	very low	49 +/-5	1.23			
Baypren® 110	very low	65 +/-7	1.23			
Baypren® 112	low	41 +/-8	1.23			
Baypren® 210	medium	43 +/-4	1.23			
Baypren® 210	medium	48 +/-4	1.23			
Baypren® 211	medium	39 +/-4	1.23			
Baypren® 230	medium	100 +/-8	1.23			
Baypren® 230	medium	108 +/-10	1.23			
XD-modified grades						
Baypren® 116	very low to low	43 +/-5	1.23	ivory-colored chips	see above	excellent mechanical properties due to formation of perfect network
Baypren® 116	very low to low	49 +/-5	1.23			
Baypren® 126	very low to low	70 +/-7	1.23			
Baypren® 216	medium	43 +/-5	1.23			
Baypren® 216	medium	49 +/-5	1.23			
Baypren® 226	medium	75 +/-6	1.23			
Special grades						
Precrosslinked grades						
Baypren® 114	very low	62 +/-10	1.23	ivory-colored chips	see above	especially designed for extrusion application
Baypren® 214	medium	55 +/-6	1.23			
Baypren® 215	medium	50 +/-6	1.23			
Sulfur-modified grades						
Baypren® 510	low to medium	42 +/-5	1.23	ivory-colored chips	see above	suitable for mastication; easy to process; for dynamic applications
Baypren® 510	low to medium	50 +/-5	1.23			
Baypren® 611	low to medium	35 +/-5	1.23			
Baypren® 611	low to medium	43 +/-6	1.23			
Baypren® 611	low to medium	48 +/-6	1.23			
Baypren® 711	low to medium	43 +/-6	1.23			
Baypren® 711	low to medium	48 +/-6	1.23			
Baypren® 712	medium	46 +/-6	1.23			

⁽¹⁾ unmassed (ISO 289)

Nomenclature of the Baypren solid rubber grades

First figure: Tendency to crystallize

1	=	low
2	=	medium
5+6+7	=	sulfur-modified grades

Second figure: Viscosity

1	=	low ("soft" grades)
2	=	medium
3	=	high ("hard" grades)

Third figure: Special properties

0	=	standard grades
1+2	=	special characteristics, e.g. regarding viscosity or crystallization
4	=	pre-crosslinked grades
5	=	pre-crosslinked and XD-modified grades
6	=	XD-modified grades

Make use of our experience!

Inventing the future together

Research and development plays a key role at LANXESS. The Technical Rubber Products business unit has research and technical centers with testing facilities on almost every continent. Whether you are looking for better compounding ideas or are thinking about developing a new product, our experts will be happy to assist you.

For direct information, please contact our technical support service. Our Baypren® experts look forward to answering your questions.

EMEA

LANXESS Deutschland GmbH
Technical Rubber Products
51369 Leverkusen
Germany
Tel: +49 214 30 45640
E-mail: andreas.roos@lanxess.com
www.lanxess.com

APAC

LANXESS Chemical (Shanghai) Co., Ltd
Technical Rubber Products
Building 8, No. 899 Zu Chong Zhi Road
Zhangjiang High-Tech Park
Shanghai, 201203
P.R. China
Tel: +86 21 51317888 236
E-mail: don.tsou@lanxess.com
www.lanxess.cn

NAFTA

LANXESS Corporation
111 RIDC Park West Drive
Pittsburgh, PA 15275-1112
USA
Tel: +1 412 809 4761
E-mail: john.dewar@lanxess.com
www.us.lanxess.com

LATAM

LANXESS Indústria de Produtos Químicos e Plásticos Ltda
Technical Rubber Products
Borrachas Sintéticas para Artigos Técnicos
R. Maria Coelho Aguiar,
215 - Sao Paulo - CEP 05804-902
Brazil
Tel: +55 11 3741 2964
E-mail: fabio.encinas@lanxess.com
www.lanxess.com.br

Sales offices worldwide:
www.sales-offices-trp.lanxess.com

www.baypren.com
www.trp.lanxess.com

Quality and safety

Quality & environmental management

Baypren® is produced under strict control regarding safety, environmental protection and quality. The whole supply chain, from production to customer service, is covered by ISO 9001 and ISO 14001 certification.

Product safety

Relevant safety data and references as well as the necessary hazard warning labels can be found in the Material Safety Data Sheet.

Food contact

Information concerning FDA and BfR compliance can be obtained on request from the Health, Safety, Environment and Quality department (HSEQ) of LANXESS.

As with any product, use of the products mentioned in this publication in a given application must be tested (including field testing, etc.) by user in advance to determine suitability.

Health and safety information:

Appropriate literature has been assembled which provides information concerning the health and safety precautions that must be observed when handling the LANXESS products mentioned in this publication. For materials mentioned which are not LANXESS products, appropriate industrial hygiene and other safety precautions recommended by their manufacturers should be followed. Before working with any of these products, you must read and become familiar with the available information on their hazards, proper use and handling. This cannot be overemphasized. Information is available in several forms, e.g., material safety data sheets and product labels. Consult your LANXESS representative in Germany or contact the Health, Safety, Environment and Quality department (HSEQ) of LANXESS Germany or - for business in the USA - the LANXESS Product Safety and Regulatory Affairs department in Pittsburgh, PA.

Regulatory Compliance Information: Some of the end uses of the products described in this publication must comply with applicable regulations, such as the FDA, BfR, NSF, USDA, and CPSC. If you have any questions on the regulatory status of these products, contact your LANXESS Corporation representative, the LANXESS Regulatory Affairs Manager in Pittsburgh, PA or the Health, Safety, Environment and Quality department (HSEQ) of LANXESS Germany.

The manner in which you use and the purpose to which you put and utilize our products, technical assistance and information (whether verbal, written or by way of production evaluations), including any suggested formulations and recommendations, are beyond our control. Therefore, it is imperative that you test our products, technical assistance and information to determine to your own satisfaction whether they are suitable for your intended uses and applications. This application-specific analysis must at least include testing to determine suitability from a technical as well as health, safety, and environmental standpoint. Such testing has not necessarily been done by us. Unless we otherwise agree in writing, all products are sold strictly pursuant to the terms of our standard conditions of sale. All information and technical assistance is given without warranty or guarantee and is subject to change without notice. It is expressly understood and agreed that you assume and hereby expressly release us from all liability, in tort, contract or otherwise, incurred in connection with the use of our products, technical assistance, and information.

Any statement or recommendation not contained herein is unauthorized and shall not bind us. Nothing herein shall be construed as a recommendation to use any product in conflict with patents covering any material or its use. No license is implied or in fact granted under the claims of any patent.

Forward-looking statements

This product information contains forward-looking statements based on current assumptions and forecasts made by the LANXESS AG management. Various known and unknown risks, uncertainties and other factors could lead to material differences between the actual future consolidated results, financial situation, development or performance of the company, and the estimates given here. The company assumes no liability to update such forward-looking statements or to adapt to future events or development.

Baypren® is a registered trademark of Bayer AG.



For the future of chemistry

LANXESS embraces its environmental responsibility and emphatically supports the Responsible Care® initiative. Responsible Care is both an ethical initiative and a commitment and aspiration to boost trust in an industry that plays a key role in improving people's living standards and quality of life.

LANXESS has supported this initiative and been one of the signatories of the "Responsible Care® Global Charter" of the International Council of Chemical Associations ICCA since 2006. With its requirements regarding health, safe use of chemical products, information policy and transparency in the industry, this Charter goes far beyond previous initiatives and makes us committed to achieving greater openness and improved public dialog.

By applying the Responsible Care® Charter, we are making our contribution to solving the world's major challenges by continually working on improving environmental protection, health & safety and quality. Our internal guidelines on quality and environmental policy ensure that the principles of the charter are central to the way we do business. After all, we at LANXESS are convinced that only sustainable development and responsible actions can ensure a successful future for chemistry.

LANXESS

Energizing Chemistry

LANXESS Deutschland GmbH
51369 Leverkusen
Germany

www.lanxess.com

Order no.: LXS-KA 029e
Edition: 2010-10
Printed in Germany

Note: The information contained in this publication is current as of October 2010. Please contact your LANXESS representative to determine if this publication has been revised.

